

material characteristics	material number / grade	SWG 2711mod							
	short designation	54NiCrMoV6mod							
	comparable grade	-							
	chemical composition - reference analysis [%]	C	Si	Mn	Cr	Mo	Ni	V	
		0.55	0.25	1.00	1.10	0.80	2.00	0.10	
	production technology	EAF/LF/VD, forging, Q+T							
	service hardness / strength converted acc. to DIN EN ISO 18265 table G.2	HB		HRC		N/mm ²		variation upon request	
		340 - 383		36 - 40.4		1093 - 1255			
	delivery condition	Q+T		295 - 383		30.4 - 40.4			935 - 1255
	maximum dimension	diameter			thickness				
≤ 1200 mm			≤ 1000 mm						
US-specification	EN 10228-3			SEP 1921					
	table 3 - type 1 - qual. class 3			group 3 - class D,d					
cleanliness	DIN 50602			ASTM E45 method A					
	K4 ≤ 20			A ≤ 1,5; B, C, D ≤ 2					

technological properties		0	1	2	3	4	5	comment	
	toughness		■	■	■				in relation to service hardness
	hot strength at working temp.		■	■	■				
	wear resistance		■	■	■	■			
	corrosion resistance	■							
	machinability		■	■				Q+T	
	polishability		■	■				ISO/SPI: N2/A-2	
	weldability		■	■				CET = 0.84 % acc. DIN EN 1011-2	
	texturability		■	■				for high texturing reliability: XPM	
	nitridability		■	■				nitriding hardness 550 - 700 HV1	
chrome-platability		■	■						

rating properties: 0 = not suitable; 1 = low; 2 = middle; 3 = good; 4 = very good; 5 = perfectly suitable

physical properties	thermal conductivity [W · m ⁻¹ · K ⁻¹]	20 °C	200 °C	300 °C	500 °C
		37.5	39.7	39.0	36.1
	coefficient of thermal expansion between 20 °C and ... [10 ⁻⁶ · K ⁻¹]	100 °C	200 °C	300 °C	500 °C
		12.5	13.1	13.4	14.0
elastic modulus [kN/mm ²]	20 °C	200 °C	300 °C	500 °C	
	212	199	192	175	


application	technology	mold making, injection molding, press-molding
	tools	large plastic molds, large die-holder
	process temperature	< 250 °C
	tool size	large-sized molds up to 650 mm thickness
	final products	injection plastic parts, press-forming plastic parts
	features	pre-hardened, high hard, for high surface requirements: XPM and XPM VICTORY ESR

SWG processing instructions	welding, texturing
-----------------------------	--------------------


heat treatment		T min [°C]	T max [°C]	medium / comment
	annealing	720	750	air
	hardening	840	870	oil, polymer
	tempering	550	680	air
	stress relieving	500	550	min. 30 °C below tempering temp.
	pre-heating before welding	300	320	
	nitriding	400	500	min. 30 °C below tempering temp.
	PVD-treating	400	500	

diagrams/ structure	CCT-diagram	yes
	tempering diagram	yes
	advice on heat treatment	pre-hardened
	microstructure	martensitic/bainitic

Tempering diagram: Average values on samples dia 25 mm x length 50 mm; hardened at 850 °C in oil

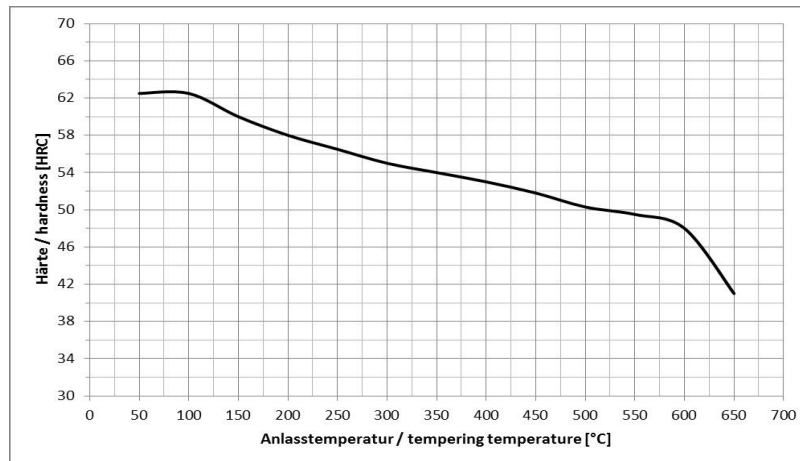

CCT-diagram

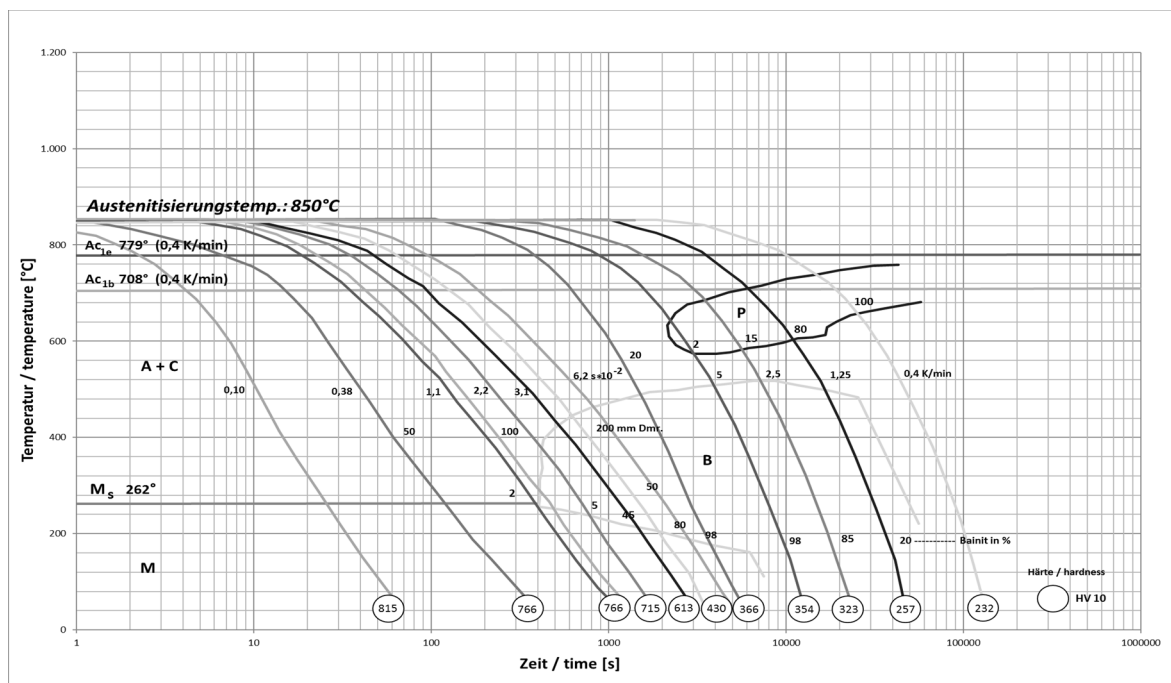

PLEASE NOTE: The information contained in this data sheet is unbinding. It merely serves the first orientation of the user. Therefore, we do not assume any liability for the correctness, completeness or up-to-dateness of such data. In case of an order, the properties of the product are exclusively subject to the provisions of the respective contract.

© Schmiedewerke Gröditz GmbH, Gröditz